

NEWS & VIEWS

Open Access

Nanophotonics shines light on hyperbolic metamaterials

Andreas Aigner¹, Judith M. Dawes², Stefan A. Maier^{1,3} and Haoran Ren²✉

Abstract

Hyperbolic metamaterials with a unique hyperbolic dispersion relation allow propagating waves with infinitely large wavevectors and a high density of states. Researchers from Korea and Singapore provide a comprehensive review of hyperbolic metamaterials, including artificially structured hyperbolic media and natural hyperbolic materials. They explain key nanophotonic concepts and describe a range of applications for these versatile materials.

Metamaterials, consisting of subwavelength meta-atoms (artificially designed unit cells of metamaterials), exhibit anomalous optical properties that cannot be found in naturally occurring materials. In the metamaterials family, hyperbolic metamaterials (HMMs) have attracted strong interest due to their unique and extreme anisotropy that renders the metamaterials to behave like a metal in one direction and a dielectric in the other. Writing in *eLight*, Dasol Lee, Sunae So, Guangwei Hu, Cheng-Wei Qiu, Junsuk Rho, and colleagues now provide a comprehensive review on HMMs from fundamentals to applications, covering both artificial metamaterials and recently discovered natural 2D materials that support hyperbolic dispersion¹.

HMMs are named after the topology of their isofrequency contour. In vacuum, the linear dispersion and isotropic behavior of propagating waves implies a spherical isofrequency contour given by the equation

$$k_x^2 + k_y^2 + k_z^2 = w^2/c^2 \quad (1)$$

where the wavevector of a propagating wave is given by $\vec{k} = [k_x, k_y, k_z]$, w is the frequency of radiation and c is the velocity of light in free space. The dispersion relation of

light in a medium with an effective permittivity tensor $\vec{\epsilon} = [\epsilon_{xx}, \epsilon_{yy}, \epsilon_{zz}]$ leads to

$$\frac{k_x^2 + k_y^2}{\epsilon_{zz}} + \frac{k_z^2}{\epsilon_{xx}} = w^2/c^2 \quad (2)$$

where the in-plane isotropic components are $\epsilon_{xx} = \epsilon_{yy}$, and out-of-plane component is ϵ_{zz} . In common materials, the isofrequency contour is represented by a spherical surface (Fig. 1a) for the isotropic case, or an ellipsoid (Fig. 1b) for the anisotropic case, respectively. However, under the condition where the signs of two components of the effective permittivity are opposite ($\epsilon_{xx} \cdot \epsilon_{zz} < 0$), the isofrequency contour becomes an unbounded hyperboloid that can support very large magnitude wavevectors². In this case, two classes of HMMs have been identified: Type-I HMMs ($\epsilon_{xx} = \epsilon_{yy} > 0, \epsilon_{zz} < 0$) have a predominantly dielectric nature (Fig. 1c); Type-II HMMs ($\epsilon_{xx} = \epsilon_{yy} < 0, \epsilon_{zz} > 0$) have a metallic nature (Fig. 1d). Type-II HMMs are highly reflective and are more absorptive than Type-I HMMs³.

This Review by Lee et al.¹ highlights different nanophotonic structures that have been developed to support hyperbolic dispersion for HMMs. These structures include multilayer HMM (Fig. 1e), nanowire HMM (Fig. 1f), hyperbolic metasurface (Fig. 1g), and natural hyperbolic materials (Fig. 1h).

Multilayer HMMs (Fig. 1e), consisting of alternating layers of metal and dielectric, have been developed to exhibit extreme anisotropy⁴. If the layer thicknesses are

Correspondence: Haoran Ren (haoran.ren@mq.edu.au)

¹Chair in Hybrid Nanosystems, NanoInstitute Munich, Faculty of Physics, Ludwig-Maximilians-University Munich, Munich 80539, Germany

²MQ Photonics Research Centre, Department of Physics and Astronomy, Macquarie University, Macquarie Park, NSW 2109, Australia


Full list of author information is available at the end of the article

© The Author(s) 2022, corrected publication 2022



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.



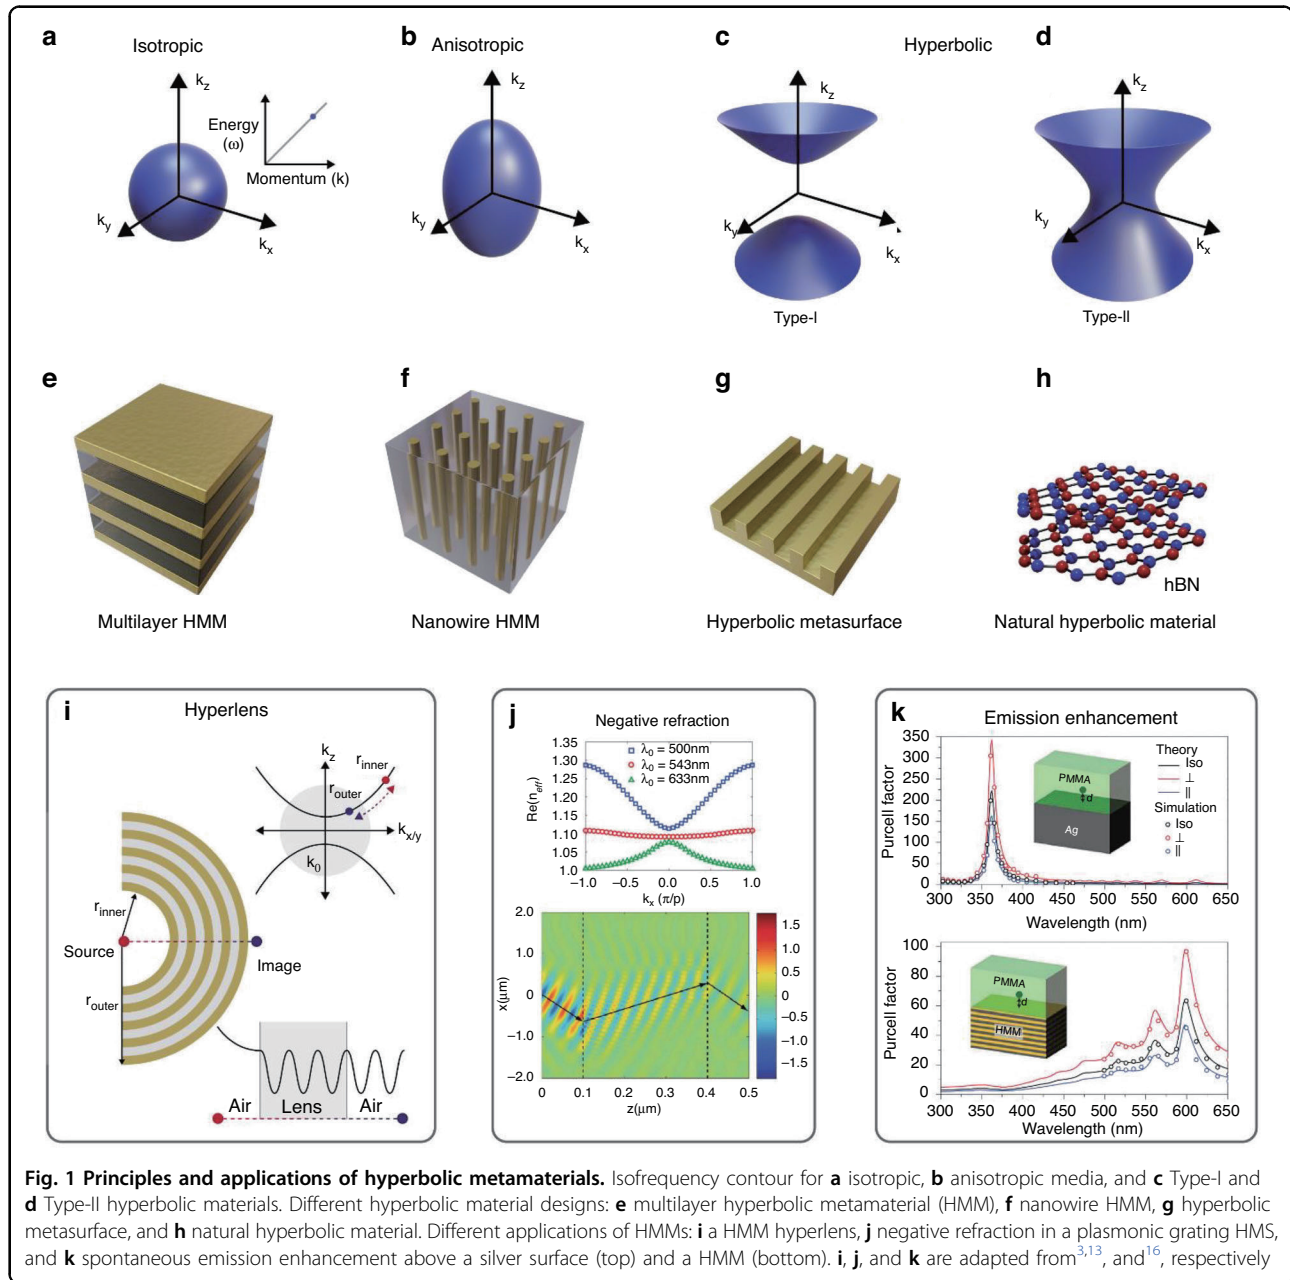

far smaller than the operating wavelength, then effective medium theory can be used to describe the macroscopic optical responses of these composite materials using homogenized effective permittivity tensors. The effective permittivity can be customized by the choice of materials and different thicknesses of metal and dielectric layers. Tuning these two parameters can yield both Type-I and Type-II multilayer HMMs, as well as effective dielectric or metallic properties⁵.

Nanowire HMMs (Fig. 1f) offer another approach to realizing HMMs, where metallic nanowires are embedded in a dielectric host medium⁶. The real part of the metal

permittivity is negative at frequencies below the plasma frequency, so the nanowire HMMs can exhibit Type-I HMM behavior without the requirement of an optical resonance. Consequently, they can operate at a relatively low loss and high transmission over a large bandwidth, although the electrochemical deposition method to date has a limited choice of materials¹.

Metasurfaces have recently transformed device design for nearly arbitrary tailored light control via arrays of ultrathin meta-atoms. Unlike the bulk multilayer HMM that generally features high Ohmic loss and a complicated multistep fabrication process,

ultrathin hyperbolic metasurfaces (HMSs) could alleviate these challenges. Metallic HMSs (Fig. 1g) exploit the control of the propagation of surface plasmon polaritons (SPPs) along the metasurface, leading to a hyperbolic dispersion of in-plane SPPs. The signs of the imaginary parts of the effective surface conductivity components are different. Consequently, HMSs can support extremely large wavevectors, as well as a large photonic density of states⁷.

Natural materials can also exhibit hyperbolic dispersion (Fig. 1h). A layered crystal structure can allow 2D conductivity and out-of-plane insulation. Since the fabrication resolution of HMMs is limited, the effective permittivity homogenization model breaks down for small wavelengths and structures close to resonance where losses are increased significantly. Furthermore, multilayer and nanowire HMMs require plasmonic metals, which are always linked with Ohmic losses. Natural HMMs overcome these limitations and can be divided into two classes. First, hyperbolic plasmon polariton materials like black phosphorus⁸ and tungsten ditelluride⁹ in which light and free electrons couple. Hyperbolic phonon polariton (HPhP) materials, like hexagonal boron nitride¹⁰, represent the second type. They are generally composed of 2D sheets of strongly coupled atoms by covalent bonds with weak van der Waals coupling between the stacked sheets. Then polaritonic coupling between photons and phonons (lattice vibrations) is highly anisotropic and out-of-plane hyperbolicity can occur. In contrast to plasmonic systems, HPhP materials are immune to Ohmic losses due to the absence of electron-electron scattering¹⁰. The operating wavelength range occurs in the mid-IR to THz region³, compared with hyperbolic plasmon polariton materials, which are used in the UV to visible region.

The hyperbolic material platforms mentioned above have led to the development of a wide field of applications. The important areas are discussed in this Review by Lee et al., and we would like to highlight a few of them.

Conventional optics is fundamentally governed by the diffraction limit. Although waves with large wavevectors can carry the information of subwavelength features, they decay exponentially in vacuum for $|\vec{k}| > k_0$ due to the limited spatial bandwidth¹¹. Therefore, an extensive scientific effort was invested in the development of hyperlenses that can overcome these limitations. Evanescent waves that are collected close to the imaged object can be turned into propagating waves with reduced wavevector¹². Fig. 1i illustrates a hyperlens consisting of a curved multilayer HMM with an inner and outer radius. When light propagates through the lens, the product of the tangential component of $|\vec{k}|$ and the radius remains constant.

If $|\vec{k}| \leq k_0$ is given, light exits the lens as a propagating wave capable of transferring subwavelength information.

Anomalous diffraction, including negative refraction, has been widely studied in HMMs and HMSs. In conventional materials the Poynting vector \vec{S} is parallel to \vec{k} for transverse magnetic (TM) modes of light. However, for light propagating along an interface between an isotropic and a hyperbolic material, \vec{S} and \vec{k} are no longer parallel and negative refraction can occur. Figure 1j shows numerical results for a HMS silver grating with a flat dispersion relation at 543 nm¹³. Besides negative refraction, other exotic photonic effects are studied in HMM like the spin Hall effect of light. It refers to typically subwavelength spin-dependent displacements of light beams at interfaces¹⁴. HMMs have proven to be good candidates for enhancing this effect with a reported polarization-dependent beam-splitting of up to 165 μm for the visible light¹⁵.

Enhancing the interaction between light and matter is one of the essential advantages of nanophotonics. HMMs are well-suited to enhancing the spontaneous emission rates of emitters either within the material, or close to their surface. Due to their open isofrequency contour, HMMs have a diverging local density of photonic states (LDOSs). Following Fermi's golden rule, the rate for spontaneous emission is proportional to the LDOS which makes HMMs ideal candidates for broadband enhancement of spontaneous emission. Figure 1k compares the Purcell factor (a measure for the spontaneous emission rate) of an emitter close to a metal surface and to a HMM¹⁶. Around the SPP resonance of the metal surface the Purcell factor increases strongly, however, this enhancement is spectrally narrow. For the multilayer HMM consisting of alternating layers of silver and silicon, multiple plasmon polariton bands broaden the bandwidth, and a high Purcell factor is achieved over the whole visible spectrum. By tuning the layer thickness and metallic filling factor of the HMM the plasmon modes can be readily controlled.

In summary, this Review by Lee et al.¹ introduces nanophotonic concepts of hyperbolic materials with the fundamental principles necessary for an insightful understanding, and presents nanofabrication and characterization details essential to experimentalists. Some future challenges and perspectives in the field are discussed as well, offering important guidance for future work.

Author details

¹Chair in Hybrid Nanosystems, NanoInstitute Munich, Faculty of Physics, Ludwig-Maximilians-University Munich, Munich 80539, Germany. ²MQ Photonics Research Centre, Department of Physics and Astronomy, Macquarie



University, Macquarie Park, NSW 2109, Australia. ³Department of Physics, Imperial College London, London SW7 2AZ, UK

Published online: 10 January 2022

References

1. Lee, D. et al. Hyperbolic metamaterials: fusing artificial structures to natural 2D materials. *eLight* **1**, 8, <https://doi.org/10.1186/s43593-021-00008-6> (2021).
2. Poddubny, A., Iorsh, I., Belov, P. & Kivshar, Y. Hyperbolic metamaterials. *Nat. Photonics* **7**, 958–967 (2013).
3. Shekhar, P., Atkinson, J. & Jacob, Z. Hyperbolic metamaterials: fundamentals and applications. *Nano Converg.* **1**, 1–17 (2014).
4. Zhukovsky, S. V., Kidwai, O. & Sipe, J. E. Physical nature of volume plasmon polaritons in hyperbolic metamaterials. *Opt. Express* **21**, 14982 (2013).
5. Choy, T. C. *Effective Medium Theory: Principles and Applications* (Oxford University Press, 2015).
6. Starko-Bowes, R. et al. Optical characterization of epsilon-near-zero, epsilon-near-pole, and hyperbolic response in nanowire metamaterials. *J. Opt. Soc. Am. B* **32**, 2074 (2015).
7. High, A. A. et al. Visible-frequency hyperbolic metasurface. *Nature* **522**, 192–196 (2015).
8. Van Veen, E. et al. Tuning two-dimensional hyperbolic plasmons in black phosphorus. *Phys. Rev. Appl.* **12**, 1 (2019).
9. Hajian, H., Rukhlenko, I. D., Hanson, G. W. & Ozbay, E. Hybrid surface plasmon polaritons in graphene coupled anisotropic van der Waals material waveguides. *J. Phys. D: Appl. Phys.* **54**, 455102 (2021).
10. Dai, S. et al. Graphene on hexagonal boron nitride as a tunable hyperbolic metamaterial. *Nat. Nanotechnol.* **10**, 682–686 (2015).
11. Lu, D. & Liu, Z. Hyperlenses and metalenses for far-field super-resolution imaging. *Nat. Commun.* **3**, 1–9 (2012).
12. Rho, J. et al. Spherical hyperlens for two-dimensional sub-diffractive imaging at visible frequencies. *Nat. Commun.* **1**, 143 (2010).
13. Liu, Y. & Zhang, X. Metasurfaces for manipulating surface plasmons. *Appl. Phys. Lett.* **103**, 141101 (2013).
14. Kim, M. et al. Total reflection-induced efficiency enhancement of the spin Hall effect of light. *ACS Photonics* **8**, 2705–2712 (2021).
15. Takayama, O. et al. Photonic spin Hall effect in hyperbolic metamaterials at visible wavelengths. *Opt. Lett.* **43**, 4602–4605 (2018).
16. Lu, D., Kan, J. J., Fullerton, E. E. & Liu, Z. Enhancing spontaneous emission rates of molecules using nanopatterned multilayer hyperbolic metamaterials. *Nat. Nanotechnol.* **9**, 48–53 (2014).

